



Cite this: DOI: 10.1039/d4cy00345d

# Au nanoparticle decoration of nanoparticulate and nanotubular TiO<sub>2</sub> using atmospheric pressure cold plasma for photocatalytic applications†

Andjelika Bjelajac,<sup>a</sup> Rada Petrovic,<sup>b</sup> Milica Stefanovic,<sup>c</sup> Adrian-Marie Phillippe,<sup>a</sup> Yves Fleming,<sup>a</sup> Jérôme Guillot,<sup>a</sup> Jean-Baptiste Chemin,<sup>a</sup> Patrick Choquet,<sup>a</sup> Joris Kadok<sup>a</sup> and Simon Bulou<sup>a</sup>

Herein, we present the effectiveness of using an atmospheric pressure dielectric barrier discharge (DBD) plasma torch for gold (Au) nanoparticle (NP) decoration of TiO<sub>2</sub> nanoparticles and nanotubes (NTs). Au NPs were synthesised using an aerosol of HAuCl<sub>4</sub>·3H<sub>2</sub>O solution that was carried with an inert gas to the near plasma post-discharge zone. Careful optimisation of the deposition parameters was done to ensure the uniform and dispersed decoration of TiO<sub>2</sub>, demonstrated by scanning and transmission electron microscopy with energy dispersive spectroscopy. The X-ray diffraction was used to confirm that the deposit was pure metallic Au. Unlike the bare TiO<sub>2</sub> nanoparticles, the samples with Au NPs showed the plasmon resonance peak in the region of 500–600 nm. The photocatalytic property enhancement of Au NP decorated TiO<sub>2</sub> structures was demonstrated: The TiO<sub>2</sub> NPs@Au nanoparticulate powder showed improved photocatalytic activity by enabling methyl orange dye degradation 35% faster than that of the pristine TiO<sub>2</sub> NPs; superior photocatalytic behaviour of TiO<sub>2</sub> NTs@Au thin films compared to bare TiO<sub>2</sub> NTs was observed in the photodegradation of stearic acid.

Received 14th March 2024,  
Accepted 3rd July 2024

DOI: 10.1039/d4cy00345d

rsc.li/catalysis

## Introduction

Today's society's biggest two concerns are about solving the energy crisis and reducing pollution. One of the strategies to deal with both is the use of photocatalytic active semiconductor metal-oxides<sup>1–3</sup> that by absorbing light create photogenerated charges used further for H<sub>2</sub> production,<sup>4</sup> CO<sub>2</sub> reduction,<sup>5</sup> water pollutant degradation<sup>6</sup> or for the self-cleaning glass coatings.<sup>7</sup> Among many, TiO<sub>2</sub> is advantageous as it is cheap, chemically stable and non-toxic.<sup>6,8</sup> However, the limitation of TiO<sub>2</sub> comes from its absorption range (anatase 3.2 eV), which is around 4% of the solar spectrum.<sup>9</sup> To overcome this, different approaches have been studied, like making nanocomposites with nanoparticles (NPs) of a noble metal, such as gold (Au).<sup>10</sup> This has been of interest due to the synergetic effect of the surface plasmon resonance (SPR) and the Schottky junction<sup>11</sup> that provides minimization

of electron/hole recombination and amplifies visible light absorption, thus, resulting in enhancement of photocatalytic activity of TiO<sub>2</sub>@Au compared to the bare TiO<sub>2</sub>.<sup>12–16</sup> The common decoration technique of TiO<sub>2</sub> with Au NPs usually implies time-consuming multisteps, and complex recovery/collection for further handling.<sup>17–19</sup> A brief overview of the reported preparation methods for photocatalytic TiO<sub>2</sub>@Au is provided in Table 1.

The most convenient and well-recognized protocols to obtain Au NPs on the surface of a semiconductor, such as TiO<sub>2</sub>, require pre-synthesis of Au NPs that can further be anchored to the surface of TiO<sub>2</sub> by simply mixing a Au colloidal solution with the semiconductor dispersion or using an appropriate amount of Au precursor for the precipitation on the TiO<sub>2</sub> surface.<sup>22,24,25</sup> The obvious disadvantage of this method is the aggregation of NPs during the mixing stage, thus reducing the efficiency of the desired application. Anchoring of Au NPs onto the chemically modified surface of semiconductors using linker molecules, thereby reducing the aggregation or coalescence of Au NPs, was proposed as a solution.<sup>26</sup> However, the subsequent removal of the linker has to be made as it can inhibit the photogenerated charge transfer and thus reduce the photocatalytic activity of TiO<sub>2</sub>@Au. Therefore, herein we explore the possibility of *in situ* formation and direct deposition of Au NPs on the TiO<sub>2</sub> surface using an aerosolized HAuCl<sub>4</sub>·3H<sub>2</sub>O solution and an

<sup>a</sup> Luxembourg Institute of Science and Technology, 28, Avenue Des Hauts-Fourneaux, L-4365 Esch-sur-Alzette, Luxembourg. E-mail: andjelika.bjelajac@list.lu

<sup>b</sup> Faculty of Technology and Metallurgy, University of Belgrade, Karnegijeva 4, 11000 Belgrade, Serbia

<sup>c</sup> Innovation Centre of the Faculty of Technology and Metallurgy, University of Belgrade, Karnegijeva 4, 11000 Belgrade, Serbia

† Electronic supplementary information (ESI) available. See DOI: <https://doi.org/10.1039/d4cy00345d>



**Table 1** Brief overview of the reported TiO<sub>2</sub>@Au preparation methods with the corresponding photocatalytic performances

TiO <sub>2</sub> @Au samples	Preparation method	Photocatalytic performances
6.1–7.6 nm Au NPs on TiO <sub>2</sub> (P25) with 0.25–1.5 wt% of Au <sup>20</sup>	Deposition–precipitation method, using urea as a basification agent and HAuCl <sub>4</sub> ·H <sub>2</sub> O as Au precursor over TiO <sub>2</sub> (P25)	The best photocatalytic performance in methyl orange dye degradation was achieved with 0.5 wt% of Au with 6 nm Au NPs over P25 having a rate constant of 0.018 ppm min <sup>-1</sup> , while for the P25 TiO <sub>2</sub> was 0.005 ppm min <sup>-1</sup>
80–100 nm wide and 5–10 nm thick TiO <sub>2</sub> nanotubes (NTs) decorated with 10 nm Au NPs <sup>13</sup>	Anodization of Ti wire to form TiO <sub>2</sub> NTs that were used as support for electrodeposition of Au NPs using HAuCl <sub>4</sub> solution	The best photocatalytic degradation of methyl orange (5.2 mg L <sup>-1</sup> , 68.1% in 30 min of UV-vis) was provided by Au/TiO <sub>2</sub> /Au/TiO <sub>2</sub> that was prepared <i>via</i> alternating anodization and electrodeposition
150 ± 10 nm wide and 1.5 μm long TiO <sub>2</sub> NTs decorated with ~20 nm Au NPs <sup>21</sup>	Anodized TiO <sub>2</sub> NTs were first soaked in a HAuCl <sub>4</sub> solution for 16 h followed by a 30 min irradiation with a UVA lamp (500 W)	TiO <sub>2</sub> NTs@Au with moderate Au content of 5.52 wt% showed the highest antibacterial activity and the highest anti-inflammatory efficiency under visible-light irradiation. The non-decorated NTs did not show any of these properties
Aggregates of ~23 nm ball-like shaped TiO <sub>2</sub> NPs (89% rutile + 11% anatase) with ~12 nm Au NPs <sup>15</sup> 7–20 nm Au NPs with 2–14 wt% loading on P25 (ref. 22)	Wet chemical preparation comprising sol–gel method for TiO <sub>2</sub> synthesis followed by citrate functionalization and adding HAuCl <sub>4</sub> ·3H <sub>2</sub> O Colloidal Au NPs were presynthesized <i>via</i> a hydrothermal method. 3-Mercaptopropionic acid was used as a capping ligand to the TiO <sub>2</sub> surface, which was removed further by annealing at 200 °C	2.5 mg of photocatalyst degraded 5 μM solution of methyl orange dye with the rate constant of 8.54 × 10 <sup>-2</sup> min <sup>-1</sup> Methyl orange degradation was achieved under visible light within 3 h with 10 nm Au NPs on P25 (6 wt% of Au)
0.5–3 wt% of 10 nm (±4 nm) Au NPs decorating 50–75 nm TiO <sub>2</sub> NPs <sup>23</sup>	Aqueous sol–gel method was employed for the decoration of TiO <sub>2</sub> with Au NPs using HAuCl <sub>4</sub> ·3H <sub>2</sub> O as Au precursor, peroxy-titanate sol and NaBH <sub>4</sub> as a reducing agent	10 ppm of RhB and 50 mg of Au@TiO <sub>2</sub> with 2 wt% of Au annealed at 450 °C provided ~95% RhB degradation in 175 min
4–10 nm Au NPs homogeneously dispersed on internal (5–8 nm wide) and external walls (8–12 nm wide) of TiO <sub>2</sub> NTs <sup>24</sup>	Hydrothermally obtained TiO <sub>2</sub> NTs were decorated with Au using HAuCl <sub>4</sub> as Au precursor	50 mL methyl orange solution (40 mg L <sup>-1</sup> ) degraded in 3 h using TiO <sub>2</sub> NTs@Au catalyst

atmospheric pressure (AP) dielectric barrier discharge (DBD) plasma torch at low temperature. The precursor solution droplets react with the plasma reactive species, leading to NP growth.<sup>27</sup> We previously demonstrated that this method is adequate for Au NP synthesis on a solid substrate, such as Si or glass.<sup>28</sup> Thus, by adapting the set-up, we obtained TiO<sub>2</sub>@Au nanocomposites with: i) powder of nanoparticulate TiO<sub>2</sub> and ii) thin films of vertically aligned TiO<sub>2</sub> nanotubes (NTs) perpendicularly oriented to the substrate.

## Experimental

### Sample preparation

As a proof-of-concept, two forms of TiO<sub>2</sub> were used for Au decoration: i) commercially available Degussa, P25 powder, consisting of 75% anatase and 25% rutile, that was dispersed in water underneath the plasma torch at a 5 cm distance. The time of deposition was varied to ensure a uniform and good dispersion of Au NPs on the TiO<sub>2</sub> surface, where 1 mg of powder in 40 mL of water for 1 h of Au deposition was chosen as the optimal; ii) the TiO<sub>2</sub> NTs films were obtained *via* anodization of titanium (Ti) foils. Ti foils (99.7%, Aldrich) were degreased by ultrasonication in acetone, ethanol, and deionized water (DI) for 30 min (each solvent 10 min). After that, titanium foils were rinsed with DI water and dried in a dryer at 100 °C for 1 h. The ordered TiO<sub>2</sub> nanotubes were

prepared by using 1 M H<sub>3</sub>PO<sub>4</sub> and 0.5% HF electrolyte. The electrochemical anodization was carried out in a two-electrode cell using a DC power source (PEQLAB EV 231), where a Ti foil was used as an anode and a thin platinum foil as a counter electrode. The distance between the Ti foil and the platinum foil was 2.5 cm. After anodization, the samples were cleaned with DI water and then dried in air. The anodized TiO<sub>2</sub> films were annealed in a furnace at 450 °C under an open atmosphere with a heating rate of 5 °C min<sup>-1</sup> for 1 h to transform from an amorphous to a crystalline nanotubular structure. Post-calcination under these conditions was performed on the as-anodized TiO<sub>2</sub> films to obtain the anatase structure, as it was shown to be much more photocatalytically active than rutile TiO<sub>2</sub>.<sup>12</sup> The annealed samples were allowed to cool down to room temperature and then used as substrates for Au NP deposition. The time of deposition was varied to avoid the excessive amount of Au *i.e.* by clogging the NTs or complete coverage of the TiO<sub>2</sub> surface, hindering the available surface for photocatalytic reactions.<sup>29,30</sup> The TiO<sub>2</sub> NT films were placed 1.5 cm below the plasma torch.

The deposition experimental setup used here consisted of a vertically placed AP torch with a coaxial DBD geometry, composed of 2 concentric hollow quartz tubes. The plasma was created between the tubes, where the inner tube was coated with Pt using the physical vapor deposition (PVD)



technique and the outer tube with Al foil. To produce the plasma, 10 slm of Ar are sent in the gap between the 2 tubes, and a sinusoidal high voltage is applied to the outer electrode (AFS generator, 52 kHz, 20 W). The exact details of the setup can be found in our previous publication.<sup>28</sup> As the Au precursor, we used a 0.25 g L<sup>-1</sup> HAuCl<sub>4</sub>·3H<sub>2</sub>O in pure ethanol. The injection was done at 0.1 ml min<sup>-1</sup> using a Hamilton 100 ml syringe and a syringe pump system. The microdroplets were produced thanks to an ultrasonic nebulizer (Sono-Tek®, 1 W,  $f = 120$  kHz). Ar was used as the carrier gas (10 slm flow rate) to carry the aerosol into the plasma near post-discharge.

### Structural characterization techniques

TEM analysis was conducted on a JEOL JEM-F200 cold FEG microscope operating at an acceleration voltage of 200 kV. Crystalline nanostructures were analyzed by direct spacing measurements on high-resolution TEM (HRTEM) images using Digital Micrograph Software from Gatan (version v.3.50.3584.0). The energy-dispersive spectroscopy (EDS) mapping was done in scanning mode (STEM). The scanning electron microscopy (SEM) investigations were carried out on a Hitachi SU-70 field emission SEM. X-ray diffraction (XRD) patterns were recorded at a fixed grazing incidence of 0.5° on a PAnalytical X'Pert Pro instrument equipped with a Cu K $\alpha$  anode (1.54184 Å) and operated at 45 kV and 40 mA.

X-Ray photoelectron spectra (XPS) were acquired using a Kratos Axis Ultra-DLD photoelectron spectrometer with a mono-chromatic Al K $\alpha$  source ( $E = 1486.6$  eV, 150 W) and a 700 × 300 mm spot size. Survey spectra were acquired using an energy resolution of 2.3 eV, whereas high-resolution spectra of the Au 4f, Ti 2p, O 1s, and C 1s regions were collected with a pass resolution of 0.6 eV. The binding energies were referenced to the position of O<sup>2-</sup> ions (at 530 eV) of the surface lattice oxygen in TiO<sub>2</sub>, as TiO<sub>2</sub> is a certain component of the system.

Photoluminescence spectroscopy was employed to study the photoinduced charge transfer between TiO<sub>2</sub> and Au NPs. For that purpose, a Microplate Reader Tecan INFINITE

M1000 PRO spectrometer was used with 360 nm excitation light.

### Photocatalytic performances analysis

To analyse the absorption properties of the samples, the diffuse reflectance spectra (DRS) were recorded using a LAMBDA 1050 UV-vis-NIR spectrophotometer from Perkin Elmer with a 100 mm integration sphere. Measurements were performed in the UV-vis spectral range (300–1500 nm).

Photocatalytic performances evaluation of P25 and P25@Au was done by following the degradation of a common organic water pollutant from the textile industry, methyl orange (MO) dye (10 ml of 5 mg L<sup>-1</sup> aqueous solution) using 7 mg of the catalyst and by measuring the intensity of the absorption peak at 468 nm. The samples were dispersed in the dye solution and first left in the dark for 30 min and then illuminated by a solar simulator (CS-100, Oriel Instruments). The sampling of the solution was done in 10 min intervals and the absorption spectra were recorded on a Microplate Reader Tecan INFINITE M1000 PRO spectrometer. To compare the samples, kinetic plots were made with  $t = f(A/A_0)$ , where  $t$  is time in minutes,  $A$  is the absorption at the time  $t$ , and  $A_0$  is the initial intensity of the absorption peak at 468 nm. A linear fitting of the  $\ln(A_0/A) = kt$  was made to approximate the kinetic rate,  $k$ .<sup>31</sup>

As a common test for TiO<sub>2</sub>-based thin film self-cleaning performances, we investigated the rate of stearic acid, CH<sub>3</sub>(CH<sub>2</sub>)<sub>16</sub>CO<sub>2</sub>H, removal. The TiO<sub>2</sub> NTs and TiO<sub>2</sub> NTs@Au thin films were analysed after deposition of 10 μl of stearic acid (SA) by spin coating (10 000 round min<sup>-1</sup> during 30 s) after dilution in methanol (2.65 mol L<sup>-1</sup>) on the substrates.<sup>32</sup> Fourier Transform Infrared (FTIR) spectrometry analyses were performed using a BRUKER VERTEX 70FTIR for the samples after 24 h in the dark and each 30 min under solar illumination. The photocatalytic efficiency of the films was estimated by calculating the  $A/A_0$ , where  $A$  is the integrated area of the adsorption peaks at about 2919 cm<sup>-1</sup> and 2848 cm<sup>-1</sup> after the time  $t$ , and  $A_0$  is the initial area measured after the samples were kept in the dark. These peaks are attributed

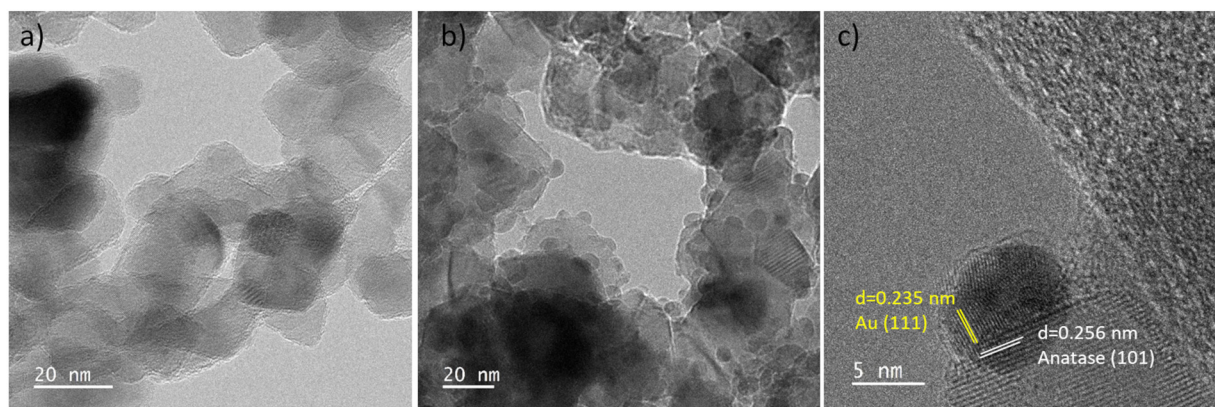


Fig. 1 TEM micrographs of: a) pristine P25, and b) and c) P25 after decoration with Au NPs.





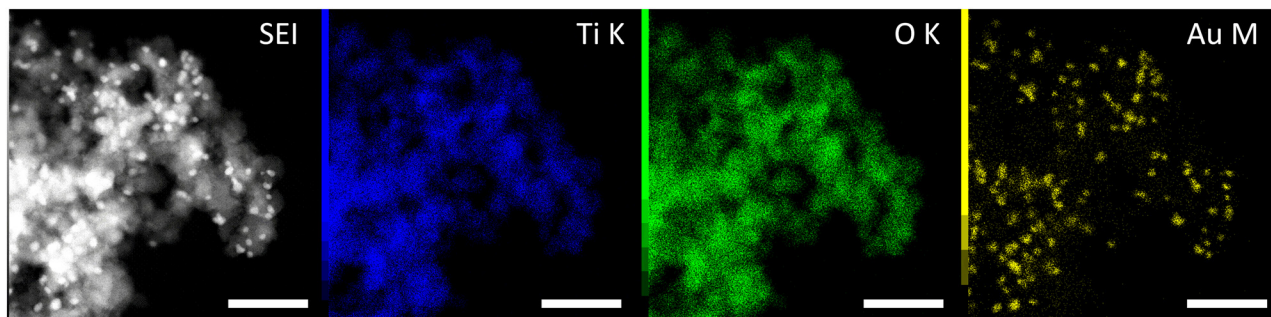


Fig. 2 STEM micrograph and corresponding EDS mappings, for Ti, O and Au, respectively (bar is 100 nm), of P25 after decoration with Au NPs.

to  $-\text{CH}_2-$  band asymmetric and symmetric stretching vibrations,<sup>33</sup> and are linked to the quantity of SA. The linear regression of the area band gives a degradation rate of zero-order ( $\text{cm}^{-1} \text{min}^{-1}$ )<sup>7</sup> illustrating the photocatalytic efficiency.

## Results and discussion

In our previous study,<sup>28</sup> we reported the optimisation of the Au NP synthesis parameters using the same plasma torch. We demonstrated how the concentration of the precursor

influences the deposition, as well as the solvent composition. As the ethanol-based precursor solution provided the best dispersion and narrow size distribution of the Au NPs, herein for the decoration of  $\text{TiO}_2$ , the same conditions were kept. The only parameter varied now was the deposition time as it directly influences the amount of Au NPs deposited. For the fixed amount of P25 dispersed in water (1 mg) for 0.5 h of Au decoration, not many Au NPs were observed (Fig. S1a†). For 1 h deposition, the Au NPs were well dispersed and of narrow size (Fig. S1b†), unlike for 1.5 h decoration (Fig. S1c†), where

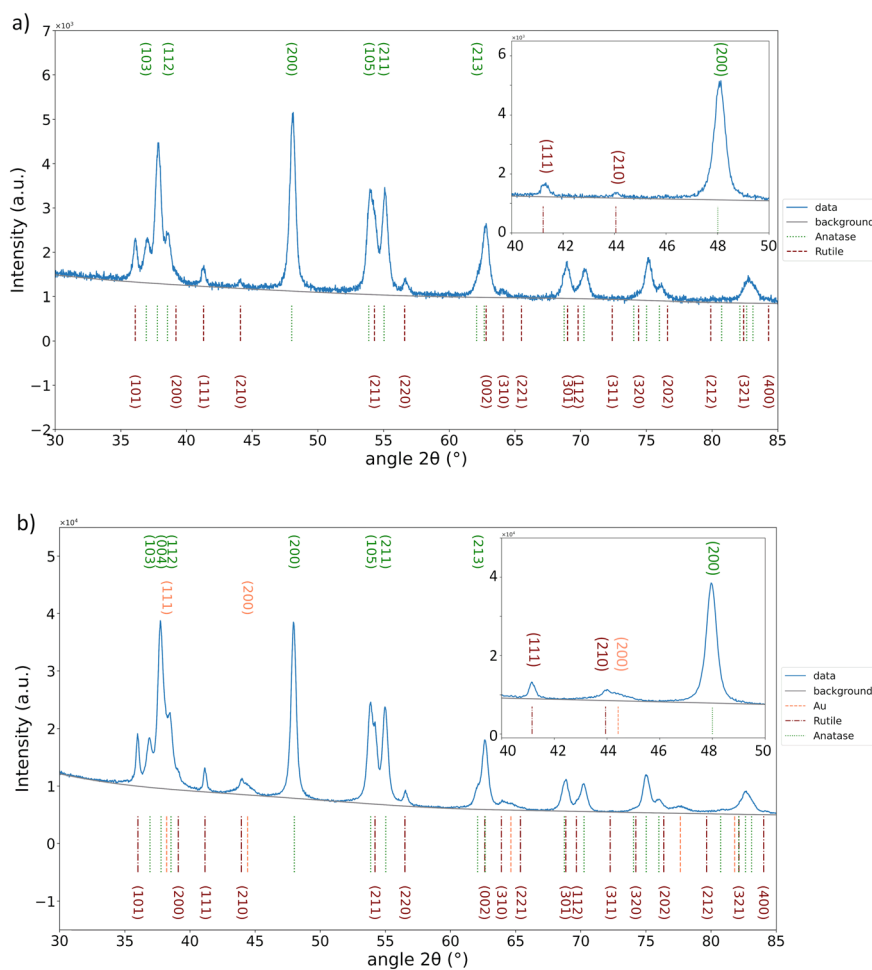


Fig. 3 GIXRD diffractograms of: a) bare P25 and b) P25@Au powder.



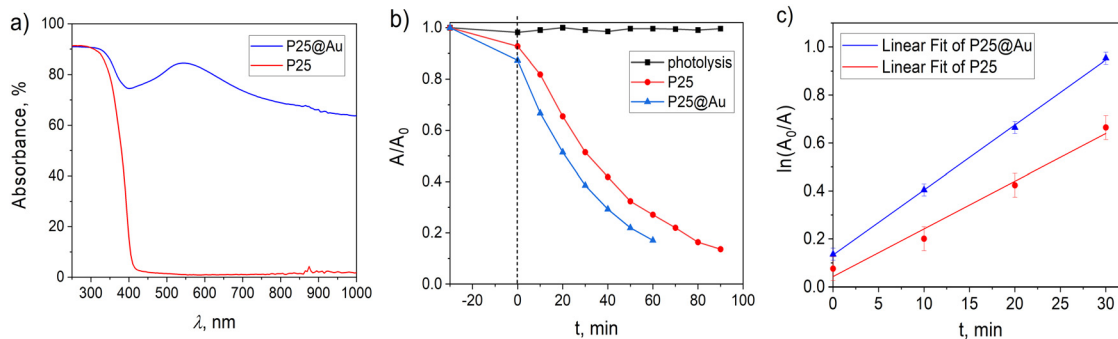


Fig. 4 a) Absorbance spectra of bare TiO<sub>2</sub> (P25) and P25@Au powders, b) photodegradation of methyl orange using bare P25 and P25@Au and c) linear fitting for estimation of the kinetic constant for P25 and P25@Au photocatalytic efficiency.

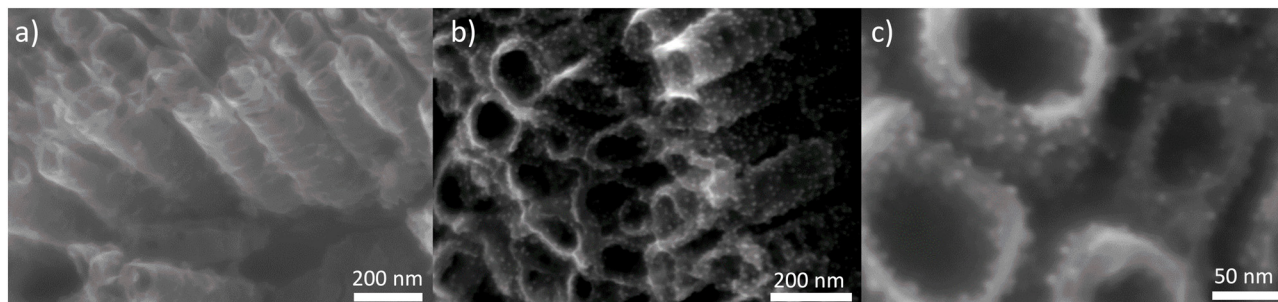


Fig. 5 SEM micrographs of: a) bare TiO<sub>2</sub> NTs, and b) and c) TiO<sub>2</sub> NTs after Au NP decoration.

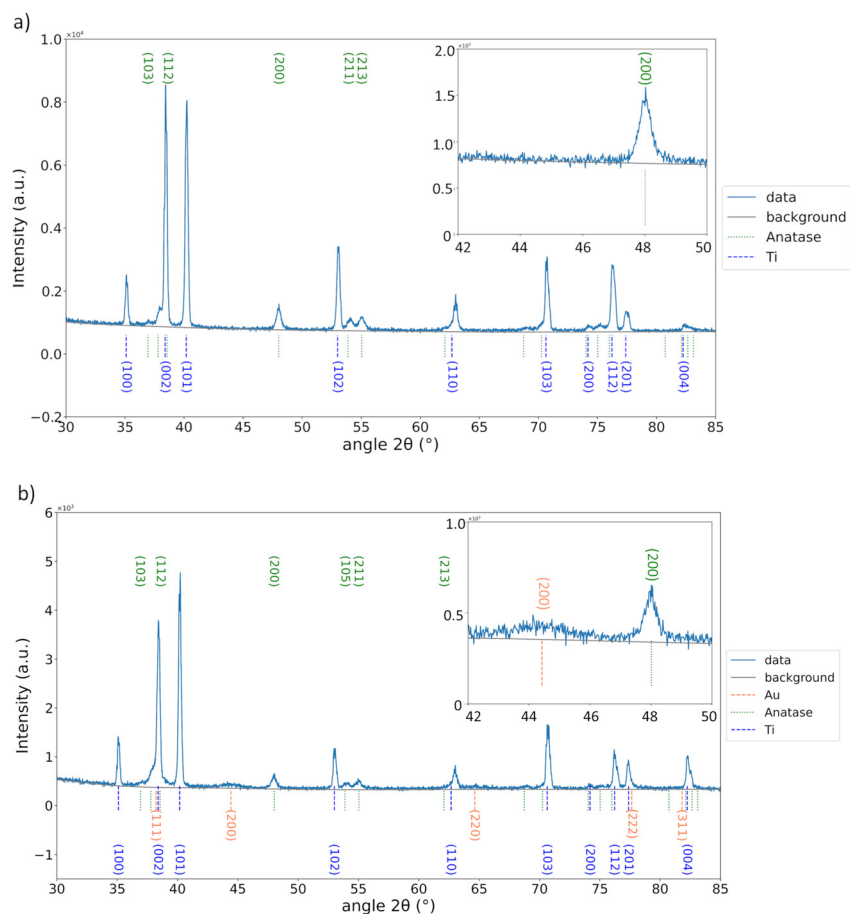


Fig. 6 GIXRD diffractograms of: a) bare TiO<sub>2</sub> NTs and b) TiO<sub>2</sub> NTs@Au thin films.



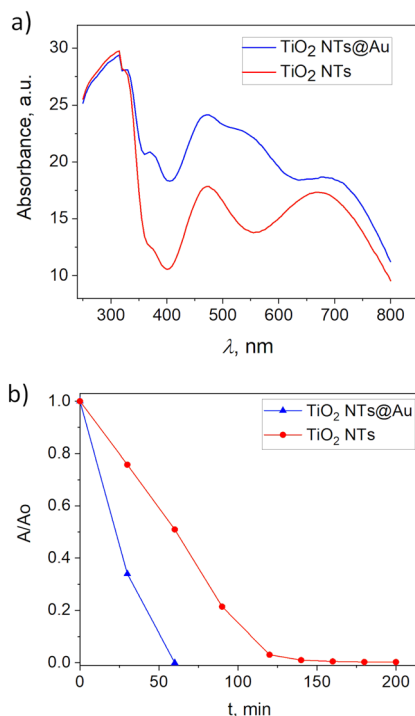


Fig. 7 a) Absorbance spectra of bare TiO<sub>2</sub> NTs and TiO<sub>2</sub> NTs@Au thin films, and b) photodegradation of stearic acid using bare TiO<sub>2</sub> NTs and TiO<sub>2</sub> NTs@Au thin films.

not just a higher amount of deposited Au was noticed, but also the NP size inhomogeneity appeared. We wanted to avoid the excessive amount of Au, as it is known that it can hinder photocatalysis, serving as recombination centres for photoelectrons and holes. Moreover, the excessive Au NPs can act as an irradiation shield of the TiO<sub>2</sub> surface and prevent the photogeneration of holes necessary for the photocatalytic degradation of a pollutant. The surface of TiO<sub>2</sub> must stay accessible for direct contact with a pollutant. Therefore, 1 h of deposition is considered enough to improve the photocatalytic performances of TiO<sub>2</sub>, but also to be detectable by means of characterisation techniques used herein (XRD, XPS, DRS). Fig. 1a presents pristine P25, whereas the representative micrographs after 1 h of Au plasma deposition are given in Fig. 1b and c. Fig. 1c shows the interplanar spacings of 0.235 nm corresponding to the Au (111) atomic plane, whereas 0.256 nm spacing corresponds to the (101) plane of the anatase phase of P25. The average Au NP size was around 5 nm. This size has been reported as beneficial for photocatalytic performances of TiO<sub>2</sub>@Au nanocomposites, compared to those with bigger Au NPs.<sup>14</sup>

The results of EDS mapping done in STEM mode of a representative portion of the P25@Au sample are presented in Fig. 2. As it can be seen, the signal for Ti and O is homogeneously distributed, corresponding to the TiO<sub>2</sub> from the P25 support, whereas the Au signal is very localized, confirming the formation of NPs on the TiO<sub>2</sub> surface. It is worth noting that a certain amount of C and Cl was detected

as it can originate from the ethanol-based HAuCl<sub>4</sub>·3H<sub>2</sub>O solution. Nevertheless, XRD showed tiny peaks corresponding to metallic gold,  $2\theta = 38.18^\circ$  matching the (111) plane and  $2\theta = 44.39^\circ$  matching the (200) planes from the JCPDS file 00-066-0091, whereas anatase and rutile identification was provided by comparing the peaks with the 04-014-8515 and 04-005-6491 files (Fig. 3). The results are in accordance with the TEM measurements.

Another confirmation of the Au decoration of P25 was seen in the DRS spectrum of P25@Au that presented an absorption shoulder in the visible range, unlike that of the bare P25 (Fig. 4a). This is due to the SPR, characteristic for Au NPs, which can lead to an enhancement of photocatalytic activity if the amount of Au is not excessive to hinder the photon flux to the TiO<sub>2</sub> surface.<sup>3,15,25,29,30,34</sup>

To evaluate the influence of the Au NP inclusion on the photocatalytic performances on the obtained TiO<sub>2</sub>@Au nanocomposites, we followed the degradation of MO. Indeed, the P25@Au sample has exhibited 85% dye degradation after 60 min, whereas pure P25 exhibited it after 80 min (Fig. 4b). The kinetic rates calculated as the slope of the linear fit of  $t = f(\ln(A_0/A))$ , were  $0.02 \text{ min}^{-1}$  for P25 and  $0.027 \text{ min}^{-1}$  for P25@Au. Similar findings were reported by Oros-Ruiz *et al.*<sup>20</sup> who used the deposition-precipitation method to prepare P25@Au with different loadings of Au NPs, demonstrating that 0.5% of Au provided the best photodegradation of MO compared to others with lower and higher amounts of Au.

Further investigations were about the decoration of anodized TiO<sub>2</sub> NTs with Au NPs under the same conditions. The variation of deposition time was done from 2 to 20 min (Fig. S2†). Again, to provide enough evidence of the Au presence, we chose 20 min as the optimal, as, *i.e.*, 2, 5 and 10 min deposition did not show XRD peaks characteristic for Au because of the scarce deposition. The 20 min decoration is clearly visible by comparing the SEM micrographs before (Fig. 5a) and after deposition, as presented in Fig. 5b and c. Au NPs preserved their shape and size as in the case of the decoration of P25. The EDS analysis affirmed the presence of Au (0.34 at%) with a negligible amount of Cl (lower than the detection limit, 0.01 at%). XRD analysis confirmed the presence of Au in the metallic phase (Fig. 6) by detecting characteristic peaks at  $2\theta = 38.18^\circ$ ,  $44.39^\circ$ ,  $65.58^\circ$ ,  $77.55^\circ$  and  $81.72^\circ$  matching the (111), (200), (220), (311) and (222) planes (JCPDS file 04-004-8456). For anatase and Ti identification, the JCPDS files 04-014-8515 and 04-007-9313 were used, respectively.

The bare TiO<sub>2</sub> NTs showed the characteristics of the plasmonic structure as reported before by having the second threshold at 547 nm.<sup>35</sup> The SPR effect of Au is visible as the absorption peak at 550 nm, whereas for pristine TiO<sub>2</sub> NTs in that wavelength, the absorption drops. It is due to the Au deposition that the photocatalytic activity of TiO<sub>2</sub> NTs (Fig. 7b) increases. The thin film with Au NPs (20 min deposition) demonstrated the complete photodegradation of stearic acid just after 1 h of illumination, whereas the bare TiO<sub>2</sub> NTs reached almost 95% after a much longer time (3.5



h). The SA degradation rates are of zero-order,  $k = (A/A_0)/t^{7,36}$  and they are calculated to be  $0.11 \text{ cm}^{-1} \text{ min}^{-1}$  and  $0.18 \text{ cm}^{-1} \text{ min}^{-1}$  for bare  $\text{TiO}_2$  NTs and  $\text{TiO}_2$  NTs@Au, respectively. Hence, a 60% increase in photocatalytic efficiency is achieved with Au NP decoration. Similarly,  $\text{TiO}_2$  NTs@Au structures reported by Xu *et al.*<sup>21</sup> demonstrated photocatalytic enhancement compared to bare  $\text{TiO}_2$  NTs. They prepared Au@ $\text{TiO}_2$  NTs by soaking the anodized  $\text{TiO}_2$  NTs films in a  $10 \text{ mg mL}^{-1}$   $\text{HAuCl}_4$  solution for 16 h. Our 20 min decoration is thus, very much competitive in terms of the preparation time.

The XPS results revealed different mechanisms of Au deposition in the case of the decoration of P25 and  $\text{TiO}_2$  NTs. As P25 powder was dispersed in water during the Au plasma deposition, the oxidation state of Ti and O did not change, as the full width at half maximum (FWHM) remained the same for both Ti and O (spectra given in Fig. 8a and b). The Au 4f spectrum corresponds well to metallic Au, but with a 0.45 eV downshift (from 83.8 eV to 83.35 eV), which indicates significant charge transfer from  $\text{TiO}_2$  (P25) to Au and thus confirms the strong Au/ $\text{TiO}_2$  interaction and formation of the Schottky junction.<sup>22</sup> However, in the case of a “dry” deposition of Au on  $\text{TiO}_2$  NTs films, two phenomena were observed: 1) plasma-induced reduction of  $\text{Ti}^{4+}$  to  $\text{Ti}^{3+}$  creating oxygen vacancies (Fig. 8d and 2) Au 4f position showed a

slight upward shift, which can be associated to metallic Au(0) particles partially being encapsulated in carbon,<sup>37–39</sup> which originates from the ethanol-based precursor solution. This phenomenon was previously described.<sup>28</sup> In addition, a downward shift of the binding energy of C 1s is observed as well, confirming the Au–C interaction, as C-based capping agents could lead to the injection and trapping of electrons from Au NPs to C.<sup>37</sup>

### Photocatalysis mechanism

The mechanism of photocatalytic degradation of MO and SA could be explained from 3 aspects:<sup>40</sup> 1)  $\text{TiO}_2$  absorbs UV light and produced electrons are being transferred to Au, thus recombination of the charges is reduced, 2) Au generates “hot” electrons by visible-light absorption due to the SPR of Au and 3) carbon encapsulating Au NPs in the case of  $\text{TiO}_2$  NT decoration, serving as electron mediators, and providing efficient isolation of electrons in  $\text{TiO}_2$  and holes in Au (Fig. 9).

1) Upon UV illumination, the electrons ( $e^-$ ) are being excited from the VB to the CB of  $\text{TiO}_2$ , leaving behind holes ( $h^+$ ). As the 5 nm Au NPs created a Schottky junction with  $\text{TiO}_2$  from P25 (proven by XPS analysis and demonstrated by HRTEM) recombination of photogenerated charges within

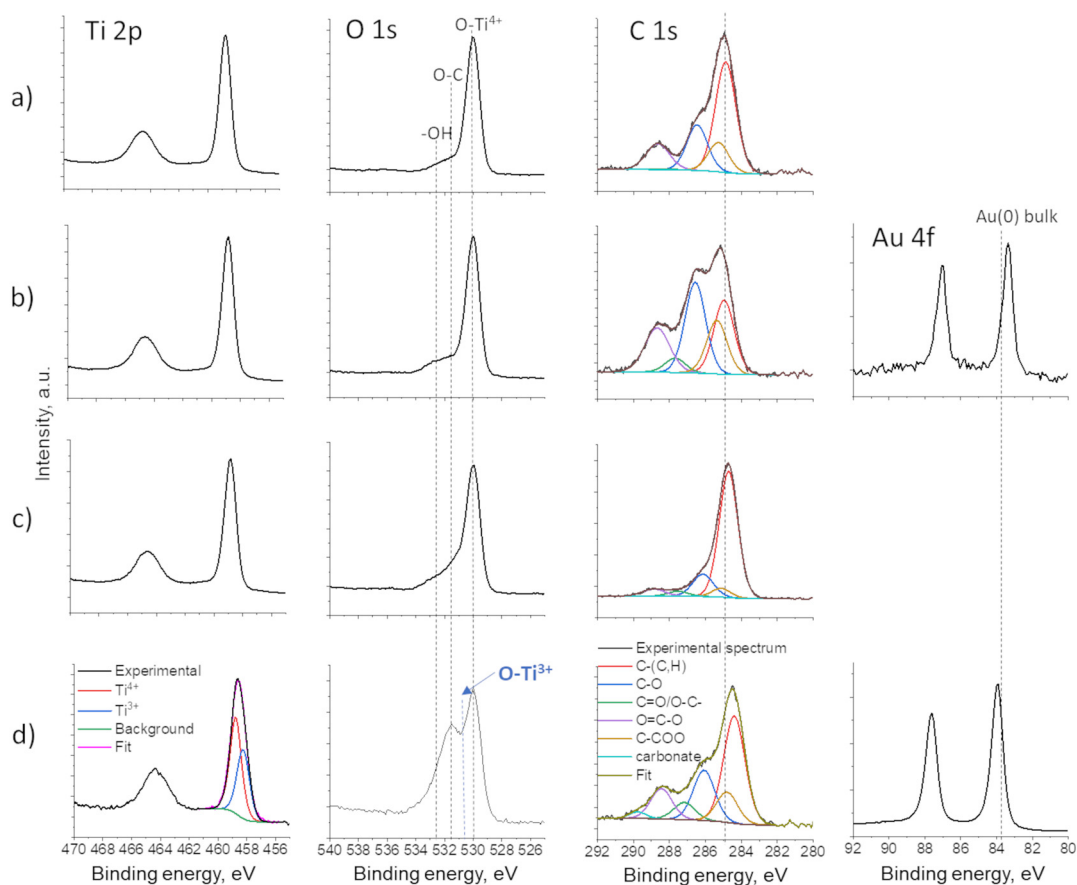


Fig. 8 XPS spectra of Ti 2p, O 1s, C 1s and Au 4f of: a) bare P25, b) P25@Au, c) bare  $\text{TiO}_2$  NTs and d)  $\text{TiO}_2$  NTs@Au thin films.





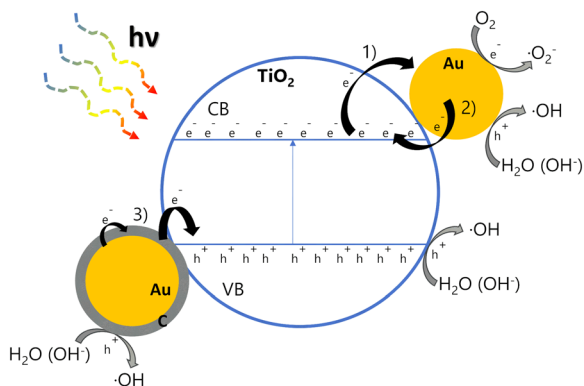


Fig. 9 Schematic illustration of the proposed mechanisms for photocatalytic degradation of MO and SA using P25@Au and TiO<sub>2</sub> NTs@Au catalysts.

TiO<sub>2</sub> is hindered due to the transfer of electron (e<sup>-</sup>) from the CB of TiO<sub>2</sub> to Au.<sup>41,42</sup> These e<sup>-</sup> can form the superoxide anions (O<sub>2</sub><sup>-</sup>) from the adsorbed O<sub>2</sub>, whereas the holes (h<sup>+</sup>) in the VB of TiO<sub>2</sub> react with H<sub>2</sub>O or OH<sup>-</sup> to produce hydroxyl radicals (·OH). Both O<sub>2</sub><sup>-</sup> and ·OH are known to cause the decomposition of the azo dyes (such as MO) and SA.

2) However, having tested the photocatalytic activity of the samples just in UV light and obtaining closely the same photocatalytic response for Au@TiO<sub>2</sub> and pristine TiO<sub>2</sub> (results not shown here), we can conclude that the main contribution of improved photocatalytic activity of Au-decorated samples is coming from the visible light absorption by Au creating additional electrons.<sup>13</sup> Under visible light irradiation, the Au plasmon induced the oscillations of free electrons to provide thermal electrons. These “hot” electrons have a higher potential energy than the Schottky barrier that is formed when Au NPs make direct physical contact with TiO<sub>2</sub> at the interface. This large potential energy difference will induce a fast and efficient transfer of “hot electrons” to the CB of TiO<sub>2</sub>.<sup>14,16</sup> The Schottky barrier at the interface also helps the transferred “hot” electrons accumulate in the TiO<sub>2</sub> CB, preventing them from traveling back to the Au NPs. This is supported by the observation of Fu *et al.*<sup>13</sup> that UV light applied on the system degradation could not produce sufficient electron-hole pairs on the photocatalyst's surface to oxidize MO molecules. Similar findings were reported by Qian *et al.*<sup>14</sup> in the photocatalytic H<sub>2</sub> production from H<sub>2</sub>O, and Verbruggen *et al.* in the case of photocatalytic degradation of SA,<sup>43</sup> where they demonstrated that the photoinduced catalytic activity of TiO<sub>2</sub>@Au was driven by visible-light excitation of the Au NPs originated from their intrinsic optical properties (SPR). Hence, in our case the visible light absorption is a key factor: it is enhanced with Au deposition with regards to pure TiO<sub>2</sub>, producing more photogenerated electrons.

3) Moreover, carbon encapsulation of Au in the case of TiO<sub>2</sub> NT decoration also contributes to the fast transfer of “hot” electrons.<sup>44</sup> The presence of carbon forms a Au-C-TiO<sub>2</sub> Z-scheme photocatalytic system,<sup>45</sup> where carbon acts as an

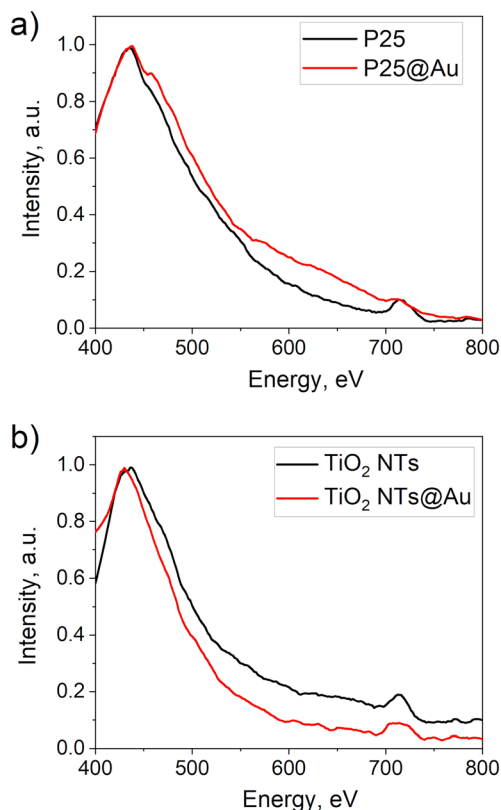


Fig. 10 PL spectra of a) P25 vs. P25@Au and b) TiO<sub>2</sub> NTs vs. TiO<sub>2</sub> NTs@Au catalysts.

electron mediator facilitating the electron flow between the two photosystems. The “hot” electrons created due to the SPR of Au are transferred to the carbon interlayer but further recombine with holes from the VB of TiO<sub>2</sub> (ref. 41) created upon UV light radiation. This proves efficient isolation of electrons in TiO<sub>2</sub> and holes in Au. Thus, Au becomes hole-rich to provide the creation of ·OH, while TiO<sub>2</sub> accumulates electrons for the creation of O<sub>2</sub><sup>-</sup>.

In the present study, the PL spectra are compared to evaluate the interaction of photogenerated charge carriers of Au coupled with TiO<sub>2</sub> (Fig. 10). In the case of P25@Au, the presence of a PL band in the visible range (550–700 nm) implies that, as assumed previously, the main mechanism for the photocatalytic reaction is due to the SPR of Au (2), but not due to the reduced recombination by the Schottky junction (1).<sup>29,46</sup> However, this band is not present in the case of TiO<sub>2</sub> NTs@Au, which could be due to carbon encapsulation of Au (mechanism 3), as noticed by Fernández-Ponce *et al.* when they measured the weakening of PL emission in the case of Au NPs capped with carbon.<sup>47</sup>

## Conclusions

Herein we demonstrated the effectiveness of an AP cold plasma torch for the *in situ* creation of ~5 nm Au NPs with direct decoration of TiO<sub>2</sub> powder (nanoparticulate P25) as well as nanotubular TiO<sub>2</sub> anodized thin films. The Au deposition





had a positive effect on the TiO<sub>2</sub> photocatalytic performances that were tested by degradation of the MO dye and SA. We believe this is mainly due to the visible light absorption of Au NPs and generation of “hot” electrons thanks to the SPR effect. It is also possible that the charge recombination is reduced by transferring the photogenerated electrons from the conduction band of TiO<sub>2</sub> to Au, as the Schottky junction. Moreover, carbon encapsulating Au NPs, in the case of TiO<sub>2</sub> NT decoration, can serve as an electron mediator, providing efficient isolation of electrons in TiO<sub>2</sub> and holes in Au. This study opens a new direction in TiO<sub>2</sub>@Au nanocomposite formation as the plasma deposition method provides the tuning of the deposition parameters. Moreover, other metallic NPs can be synthesised using the same method and the decoration of a support of interest can be investigated further.

## Data availability

The data supporting this article have been included as part of the ESI.†

## Author contributions

Andjelika Bjelajac: conceptualization, investigation, and methodology; Rada Petrovic: formal analysis and investigation; Milica Stefanovic: methodology, formal analysis, and investigation; Adrian-Marie Phillipe: formal analysis and investigation; Yves Fleming: formal analysis and investigation; Jérôme Guillot: formal analysis and investigation; Jean-Baptiste Chemin: formal analysis; Joris Kadok: formal analysis and investigation; Patrick Choquet: funding acquisition and resources; Simon Bulou: funding acquisition, investigation, methodology, project administration, supervision, and validation.

## Conflicts of interest

There are no conflicts to declare.

## Acknowledgements

The authors from LIST gratefully acknowledge the Luxembourg National Research Fund (FNR) for the financial support through the PlaSprayNano project grant (C20/MS/14701998/PlaSprayNano/bulou). The authors from the University of Belgrade gratefully acknowledge the Ministry of Science, Technological Development and Innovation of the Republic of Serbia for the financial support through the project contract no. 451-03-65/2024-03/200135 and 451-03-66/2024-03/200287.

## Notes and references

- H. Kumari, S. Suman, R. Ranga and S. Chahal, *Water, Air, Soil Pollut.*, 2023, **234**, 1–46.
- F. T. Geldasa, M. A. Kebede, M. W. Shura and F. G. Hone, *RSC Adv.*, 2023, **13**, 18404–18442.
- B. Xue, *et al.*, *Chemosphere*, 2023, **332**, 138829.
- A. Kudo and Y. Miseki, *Chem. Soc. Rev.*, 2009, **38**, 253–278.
- S. Xie, Q. Zhang, G. Liu and Y. Wang, *Chem. Commun.*, 2016, **52**, 35–59.
- C. Díaz, M. Segovia and M. L. Valenzuela, *Photochem.*, 2022, **2**, 609–627.
- S. Alofi, C. O. Rourke and A. Mills, *J. Photochem. Photobiol., A*, 2023, **435**, 114273.
- H. Lin, C. P. Huang, W. Li, C. Ni, S. I. Shah and Y. H. Tseng, *Appl. Catal., B*, 2006, **68**, 1–11.
- M. Humayun, F. Raziq, A. Khan and W. Luo, *Green Chem. Lett. Rev.*, 2018, **11**, 86–102.
- Q. Wang, *et al.*, *ChemNanoMat*, 2022, **8**, e202100396.
- L. Jing, W. Zhou, G. Tian and H. Fu, *Chem. Soc. Rev.*, 2013, **42**, 9509–9549.
- M. Murdoch, *et al.*, *Nat. Chem.*, 2011, **3**, 489–492.
- C. Fu, M. Li, H. Li, C. Li, X. Guo Wu and B. Yang, *J. Alloys Compd.*, 2017, **692**, 727–733.
- K. Qian, *et al.*, *J. Am. Chem. Soc.*, 2014, **136**, 9842–9845.
- J. Singh, K. Sahu, B. Satpati, J. Shah, R. K. Kotnala and S. Mohapatra, *J. Phys. Chem. Solids*, 2019, **135**, 109100.
- W. Wang, *et al.*, *Chem. Eng. J.*, 2023, **455**, 140909.
- Q. Fang, *et al.*, *ACS Appl. Energy Mater.*, 2019, **2**, 2654–2661.
- Z. H. N. Al-Azri, *et al.*, *J. Catal.*, 2015, **329**, 355–367.
- R. J. Wong, *et al.*, *Catal. Sci. Technol.*, 2016, **6**, 8188–8199.
- S. Oros-Ruiz, *et al.*, *Catal. Commun.*, 2012, **21**, 72–76.
- W. Xu, *et al.*, *J. Electroanal. Chem.*, 2019, **842**, 66–73.
- D. Ding, K. Liu, S. He, C. Gao and Y. Yin, *Nano Lett.*, 2014, **14**, 6731–6736.
- S. K. Khore, S. R. Kadam, S. D. Naik, B. B. Kale and R. S. Sonawane, *New J. Chem.*, 2018, **42**, 10958–10968.
- Y. Gao, *et al.*, *Mater. Lett.*, 2014, **130**, 1–4.
- J. Nie, J. Schneider, F. Sieland, S. Xia and D. W. Bahnemann, *J. Photochem. Photobiol., A*, 2018, **2**, 111–117.
- C. Ray and T. Pal, *J. Mater. Chem. A*, 2017, **5**, 9465–9487.
- E. Nadal, *et al.*, *Nanotechnology*, 2021, **32**, 175601.
- A. Bjelajac, *et al.*, *Nanoscale Adv.*, 2023, **5**, 2573–2582.
- C. Feng, Z. Yu, H. Liu, K. Yuan and X. Wang, *Appl. Phys. A: Mater. Sci. Process.*, 2017, **123**, 1–9.
- C. Liu, X. Lu, Y. Tong, J. Z. Zhang, Y. Hsu and Y. Li, *Nano Lett.*, 2013, **13**, 3817–3823.
- A. Bjelajac, I. Florea, M. Zamfir, S. Tusseau Nenez and C.-S. Cojocaru, *Nanotechnology*, 2023, **34**, 495704.
- B. Dey, *et al.*, *Sci. Rep.*, 2020, **10**(21952), 1–12.
- D. Li, *et al.*, *Appl. Surf. Sci.*, 2019, **466**, 63–69.
- G. Yang, *et al.*, *Appl. Catal., B*, 2018, **234**, 260–267.
- A. Bjelajac, *et al.*, *Ceram. Int.*, 2015, **41**, 7048–7053.
- T. W. Liao, *et al.*, *Nanomaterials*, 2018, **8**, 1–9.
- A. Patnaik and C. Li, *Appl. Surf. Sci.*, 1999, **140**, 197–203.
- F. Gao and Y. Xu, *J. Appl. Polym. Sci.*, 1997, **65**, 931–938.
- X. Duan, *et al.*, *Chem. Sci.*, 2016, **7**, 3181–3187.
- D. Hao, *et al.*, *Energy Mater. Adv.*, 2021, **2021**, 1–12.
- X. Dai, *et al.*, *J. Phys. Chem. C*, 2019, **123**, 20325–20332.
- L. G. Devi and R. Kavitha, *Appl. Surf. Sci.*, 2016, **360**, 601–622.



- 43 S. W. Verbruggen, *et al.*, *Appl. Catal., B*, 2014, **156–157**, 116–121.
- 44 S. Chen, X. Li, W. Zhou, S. Zhang and Y. Fang, *Appl. Surf. Sci.*, 2018, **466**, 254–261.
- 45 B. Ng, L. K. Putri, X. Y. Kong, Y. W. Teh and P. Pasbakhsh, *Adv. Sci.*, 2020, **7**, 1903171.
- 46 M. Alsaidi, F. A. Azeez, L. A. Al and H. Adel, *Environ. Sci. Pollut. Res.*, 2023, **30**, 17951–17964.
- 47 C. Fernández-Ponce, J. P. Muñoz-Miranda, D. M. de los Santos, E. Aguado, F. García-Cozar and R. Litrán, *J. Nanopart. Res.*, 2018, **20**, 305.

